

DYNAMIC CRACK PROPAGATION BETWEEN TWO BONDED ORTHOTROPIC PLATES

M. S. MATBULY

Received 30 June 2003 and in revised form 30 August 2003

The problem of crack propagation along the interface of two bonded dissimilar orthotropic plates is considered. Using Galilean transformation, the problem is reduced to a quasistatic one. Then, using Fourier transforms and asymptotic analysis, the problem is reduced to a pair of singular integral equations with Cauchy-type singularity. These equations are solved using Gauss-Chebyshev quadrature formulae. The dynamic stress intensity factors are obtained in closed form expressions. Furthermore, a parametric study is introduced to investigate the effect of crack growth rate and geometric and elastic characteristics of the plates on values of dynamic stress intensity factors.

1. Introduction

Composite materials have been extensively employed in many engineering fields such as mechanical and aerospace structures. When the material used as member of such structures contains a crack, it is seriously necessary to study the stress field distribution at the immediate vicinity of crack tips. The inertia action must be considered when the applied loads or crack length depend on time. Also, the most frequently observed phenomenon in the experiments shows that the crack growth rate is constant during the extending history except in the final unstable or arresting stage [11]. So, the elastodynamic analysis of a moving crack, with constant velocity, is one of the most important problems in fracture mechanics. The dynamic stress intensity factors (DSIF) play a key role in characterizing the fracture behaviour of such problems. Thus, analytical determination of DSIF in predicting the fracture cannot be overemphasized.

In general, there are two approaches for analytical determination of DSIF. The first one employs the integral transforms and asymptotic analysis to reduce the problem to that of a system of singular integral equations [1, 3, 10, 15, 20, 22, 23]. The second approach employs complex analysis to reduce the problem to that of a system of Riemann-Hilbert problems [12, 13, 14, 19].

The present work is concerned with elastodynamic stress disturbance problem of a moving Griffith crack with constant velocity. The crack is located at the interface of two

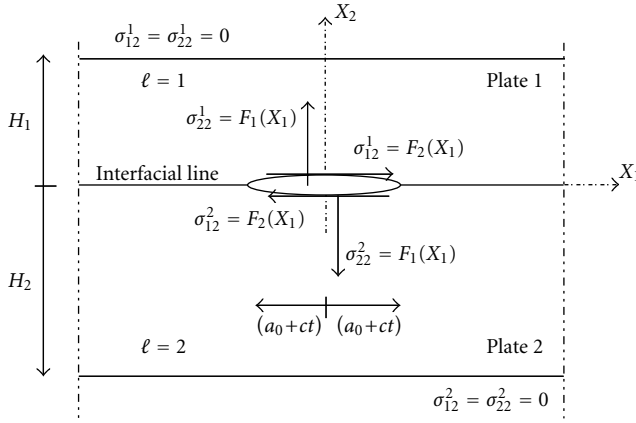


Figure 1.1. Two bonded dissimilar plates containing moving interfacial crack.

bonded dissimilar orthotropic plates, as shown in Figure 1.1. Each plate possesses a finite width and is subjected to a static stress distribution along crack surfaces. This is the main difference between the present work and previous ones [1, 3, 4, 6, 7, 8, 10, 12, 13, 14, 15, 19, 20, 22, 23], which were concerned only with plates of infinite widths. The governing equations of the problem are described. Then, Fourier transforms and asymptotic analysis are employed to reduce the solution of the problem to that of a system of first-kind singular integral equations with Cauchy-type singularity. These are solved numerically according to the algorithm in [17]. Then, closed-form expressions for the asymptotic stress field distribution at the immediate vicinity of crack tips are obtained.

2. Governing equations

Assuming that the Cartesian coordinate axes are the axes of symmetry of the elastic materials, the displacement equations of motion for orthotropic plates are [3]

$$\begin{aligned}
 C_{11}^{\ell} \frac{\partial^2 U_1^{\ell}}{\partial X_1^2} + C_{66}^{\ell} \frac{\partial^2 U_1^{\ell}}{\partial X_2^2} + [C_{12}^{\ell} + C_{66}^{\ell}] \frac{\partial^2 U_2^{\ell}}{\partial X_1 \partial X_2} &= m^{\ell} \frac{\partial^2 U_1^{\ell}}{\partial t^2}, \\
 C_{66}^{\ell} \frac{\partial^2 U_2^{\ell}}{\partial X_1^2} + C_{22}^{\ell} \frac{\partial^2 U_2^{\ell}}{\partial X_2^2} + [C_{12}^{\ell} + C_{66}^{\ell}] \frac{\partial^2 U_1^{\ell}}{\partial X_1 \partial X_2} &= m^{\ell} \frac{\partial^2 U_2^{\ell}}{\partial t^2},
 \end{aligned}
 \tag{2.1}$$

where ℓ is a superscript ($\ell = 1$ for orthotropic material in $X_2 > 0$, while $\ell = 2$ for orthotropic material in $X_2 < 0$), as shown in Figure 1.1; U_j^{ℓ} ($j = 1, 2$) are the displacement components in direction of X_1 and X_2 , respectively; C_{ij}^{ℓ} ($i, j = 1, 2$) and C_{66}^{ℓ} are the elastic constants of orthotropic plate materials; and m^{ℓ} and t are the material mass density and time, respectively.

The boundary conditions along the interface of plates are

$$\begin{aligned}
 \lim_{X_2 \rightarrow 0^+} \sigma_{22}^1(X_1, X_2, t) &= \lim_{X_2 \rightarrow 0^-} \sigma_{22}^2(X_1, X_2, t) = F_1(X_1), \\
 \lim_{X_2 \rightarrow 0^+} \sigma_{12}^1(X_1, X_2, t) &= \lim_{X_2 \rightarrow 0^-} \sigma_{12}^2(X_1, X_2, t) = F_2(X_1),
 \end{aligned}
 \quad |X_1| < a_0 + d,$$

$$\begin{aligned}
 \lim_{X_2 \rightarrow 0^+} U_1^1(X_1, X_2, t) &= \lim_{X_2 \rightarrow 0^-} U_1^2(X_1, X_2, t), \\
 \lim_{X_2 \rightarrow 0^+} U_2^1(X_1, X_2, t) &= \lim_{X_2 \rightarrow 0^-} U_2^2(X_1, X_2, t), \\
 \lim_{X_2 \rightarrow 0^+} \sigma_{22}^1(X_1, X_2, t) &= \lim_{X_2 \rightarrow 0^-} \sigma_{22}^2(X_1, X_2, t), \\
 \lim_{X_2 \rightarrow 0^+} \sigma_{12}^1(X_1, X_2, t) &= \lim_{X_2 \rightarrow 0^-} \sigma_{12}^2(X_1, X_2, t),
 \end{aligned}
 \quad |X_1| > a_0 + d,$$

(2.2)

where a_0 is the initial half crack length, and $d = |c|t$, where c is the magnitude of crack propagation velocity. Moreover, $F_i(X_1)$ ($i = 1, 2$) are known functions. They represent the applied static stress along crack surfaces; $F_1(-X_1) = F_1(X_1)$ and $F_2(-X_1) = -f_2(-X_1)$.

The boundary conditions along the external boundaries are

$$\begin{aligned}
 \sigma_{12}^1(X_1, H_1, t) &= \sigma_{22}^1(X_1, H_1, t) = \sigma_{12}^2(X_1, -H_2, t) \\
 &= \sigma_{22}^2(X_1, -H_2, t) = 0, \quad |X_1| < \infty,
 \end{aligned}$$

(2.3)

where H_1 and H_2 are as shown in [Figure 1.1](#).

Using Galilean transformation: $x = (X_1 - ct)/a_0$, $y = X_2/a_0$, and $t = t$, the governing equations (2.1), (2.2), and (2.3) can be reduced to a quasistatic form as follows:

$$\begin{aligned}
 \frac{\partial^2 u^\ell}{\partial x^2} + a_1^\ell \frac{\partial^2 v^\ell}{\partial x \partial y} + a_2^\ell \frac{\partial^2 u^\ell}{\partial y^2} &= 0, \\
 \frac{\partial^2 v^\ell}{\partial x^2} + b_1^\ell \frac{\partial^2 u^\ell}{\partial x \partial y} + b_2^\ell \frac{\partial^2 v^\ell}{\partial y^2} &= 0,
 \end{aligned}
 \quad (\ell = 1, 2)$$

(2.4)

where

$$u^\ell(x, y) = \frac{U_1^\ell(X_1, X_2, t)}{a_0}, \quad v^\ell(x, y) = \frac{U_2^\ell(X_1, X_2, t)}{a_0},$$

(2.5a)

$$a_1^\ell = \frac{C_{12}^\ell + C_{66}^\ell}{C_{11}^\ell [1 - (M_1^\ell)^2]}, \quad a_2^\ell = \frac{C_{66}^\ell}{C_{11}^\ell [1 - (M_1^\ell)^2]},$$

(2.5b)

$$b_1^\ell = \frac{C_{12}^\ell + C_{66}^\ell}{C_{66}^\ell [1 - (M_2^\ell)^2]}, \quad b_2^\ell = \frac{C_{22}^\ell}{C_{66}^\ell [1 - (M_2^\ell)^2]},$$

(2.5c)

$$M_j^\ell = \frac{c}{V_j^\ell} \quad (j = 1, 2), \quad V_1^\ell = \sqrt{\frac{C_{11}^\ell}{m^\ell}}, \quad V_2^\ell = \sqrt{\frac{C_{66}^\ell}{m^\ell}}.$$

(2.5d)

Furthermore, the values of Mach numbers M_j^ℓ ($\ell, j = 1, 2$) are assumed to be less than unity for subsonic crack propagation.

The boundary conditions for the reduced quasistatic problem can be expressed as follows:

$$\begin{aligned} \lim_{y \rightarrow 0^+} \sigma_{yy}^1(x, y) &= \lim_{y \rightarrow 0^-} \sigma_{yy}^2(x, y) = f_1(x), \\ \lim_{y \rightarrow 0^+} \sigma_{xy}^1(x, y) &= \lim_{y \rightarrow 0^-} \sigma_{xy}^2(x, y) = f_2(x), \quad |x| < 1, \end{aligned} \quad (2.6)$$

$$\begin{aligned} \lim_{y \rightarrow 0^+} u^1(x, y) &= \lim_{y \rightarrow 0^-} u^2(x, y), \\ \lim_{y \rightarrow 0^+} v^1(x, y) &= \lim_{y \rightarrow 0^-} v^2(x, y), \quad |x| > 1, \end{aligned} \quad (2.7)$$

$$\begin{aligned} \lim_{y \rightarrow 0^+} \sigma_{yy}^1(x, y) &= \lim_{y \rightarrow 0^-} \sigma_{yy}^2(x, y), \\ \lim_{y \rightarrow 0^+} \sigma_{xy}^1(x, y) &= \lim_{y \rightarrow 0^-} \sigma_{xy}^2(x, y), \quad |x| > 1, \end{aligned} \quad (2.8)$$

$$\sigma_{yy}^1(x, h_1) = \sigma_{xy}^1(x, h_1) = \sigma_{yy}^2(x, -h_2) = \sigma_{xy}^2(x, -h_2) = 0, \quad |x| < \infty, \quad (2.9)$$

where

$$\begin{aligned} \sigma_{xy}^\ell &= \frac{\sigma_{12}^\ell}{Q}, \quad \sigma_{yy}^\ell = \frac{\sigma_{22}^\ell}{Q}, \quad Q = \sqrt{C_{66}^1 C_{66}^2}, \\ h_\ell &= \frac{H_\ell}{a_0} \quad (\ell = 1, 2). \end{aligned} \quad (2.10)$$

3. Solution of the problem

Decoupling (2.4) then employing Fourier sine (cosine) transforms with respect to x , one can find that

$$\begin{aligned} u^\ell(x, y) &= \frac{1}{\pi} \sum_{j=1}^4 \left(\int_0^\infty A_j^\ell(\alpha) e^{\alpha r_j^\ell y} \sin \alpha x \, d\alpha \right), \\ v^\ell(x, y) &= \frac{1}{\pi} \sum_{j=1}^4 \left(\int_0^\infty k_j^\ell A_j^\ell(\alpha) e^{\alpha r_j^\ell y} \cos \alpha x \, d\alpha \right), \end{aligned} \quad (\ell = 1, 2) \quad (3.1)$$

where α is the transform variable, $A_j^\ell(\alpha)$ ($\ell = 1, 2$ and $j = 1, 4$) are unknown functions, and r_j^ℓ ($\ell = 1, 2$ and $j = 1, 4$) are the real distinct roots of

$$f_1^\ell r^4 - 2f_2^\ell r^2 + 1 = 0 \quad (\ell = 1, 2), \quad (3.2)$$

provided that

$$f_1^\ell = a_2^\ell b_2^\ell, \quad 2f_2^\ell = a_2^\ell + b_2^\ell - a_1^\ell b_1^\ell, \quad f_2^\ell > \sqrt{f_1^\ell}, \quad f_1^\ell > 0, \quad (3.3)$$

$$k_j^\ell = \frac{a_2^\ell (r_j^\ell)^2 - 1}{a_1^\ell r_j^\ell} \quad (\ell = 1, 2, \quad j = 1, 4). \quad (3.4)$$

From the stress-displacement relationship of orthotropic materials [9], one can get

$$\begin{aligned}\sigma_{xy}^\ell(x, y) &= \frac{C_{66}^\ell}{Q} \left[\frac{\partial v^\ell}{\partial x} + \frac{\partial u^\ell}{\partial y} \right] \\ &= \frac{1}{\pi} \sum_{j=1}^4 \left(\int_0^\infty \alpha p_j^\ell A_j^\ell(\alpha) e^{\alpha r_j^\ell y} \sin \alpha x d\alpha \right) \quad (\ell = 1, 2), \\ \sigma_{yy}^\ell(x, y) &= \frac{1}{Q} \left[C_{12}^\ell \frac{\partial u^\ell}{\partial x} + C_{22}^\ell \frac{\partial v^\ell}{\partial y} \right] \\ &= \frac{1}{\pi} \sum_{j=1}^4 \left(\int_0^\infty \alpha o_j^\ell A_j^\ell(\alpha) e^{\alpha r_j^\ell y} \cos \alpha x d\alpha \right) \quad (\ell = 1, 2),\end{aligned}\tag{3.5}$$

where

$$p_j^\ell = \frac{C_{66}^\ell [r_j^\ell - k_j^\ell]}{Q}, \quad o_j^\ell = \frac{[C_{12}^\ell + C_{22}^\ell r_j^\ell k_j^\ell]}{Q}.\tag{3.6}$$

On suitable substitution from (2.9) into (3.5), one can find that

$$A_m^\ell(\alpha) = \sum_{j=3}^4 L_{jm}^\ell e^{\alpha \beta_{jm}^\ell} A_j^\ell(\alpha) \quad (m, \ell = 1, 2),\tag{3.7}$$

where

$$\beta_{jm}^\ell = \begin{cases} h_1(r_j^\ell - r_m^\ell) & \text{for } \ell = 1 \\ h_2(r_m^\ell - r_j^\ell) & \text{for } \ell = 2 \end{cases} \quad (m = 1, 2, j = 3, 4),\tag{3.8}$$

$$L_{jm}^\ell = \frac{\sum_{n=1}^2 (-1)^n (1 - \delta_{nm}) [p_n^\ell o_j^\ell - p_j^\ell o_n^\ell]}{p_1^\ell o_2^\ell - p_2^\ell o_1^\ell} \quad (\ell, m = 1, 2, j = 3, 4),\tag{3.9}$$

δ_{nm} is the Kronecker delta.

Substituting (3.5) and (3.7) into (2.8), one can find that

$$\begin{aligned}A_3^2(\alpha) &= \frac{E_4^2 D_3^1 - D_4^2 E_3^1}{\Delta} A_3^1(\alpha) + \frac{E_4^2 D_4^1 - D_4^2 E_4^1}{\Delta} A_4^1(\alpha), \\ A_4^2(\alpha) &= \frac{D_3^2 E_3^1 - E_3^2 D_3^1}{\Delta} A_3^1(\alpha) + \frac{D_3^2 E_4^1 - E_3^2 D_4^1}{\Delta} A_4^1(\alpha),\end{aligned}\tag{3.10}$$

where

$$\begin{aligned}\Delta &= D_3^2 E_4^2 - D_4^2 E_3^2, \\ D_j^\ell &= p_j^\ell + \sum_{m=1}^2 p_m^\ell L_{jm}^\ell e^{\alpha \beta_{jm}^\ell}, \quad E_j^\ell = o_j^\ell + \sum_{m=1}^2 o_m^\ell L_{jm}^\ell e^{\alpha \beta_{jm}^\ell} \quad (\ell = 1, 2, j = 3, 4).\end{aligned}\tag{3.11}$$

The boundary conditions (2.6) and (2.7) in conjunction with (3.7), (3.8), (3.9), (3.10), and (3.11) lead to

$$\frac{1}{\pi} \int_0^{\infty} \alpha [E_3^1 A_3^1(\alpha) + E_4^1 A_4^1(\alpha)] \cos \alpha x d\alpha = f_1(x), \quad |x| < 1, \quad (3.12)$$

$$\frac{1}{\pi} \int_0^{\infty} \alpha [D_3^1 A_3^1(\alpha) + D_4^1 A_4^1(\alpha)] \sin \alpha x d\alpha = f_2(x),$$

$$\frac{1}{\pi} \int_0^{\infty} \alpha [\tau_1(\alpha) A_3^1(\alpha) + \tau_2(\alpha) A_4^1(\alpha)] \sin \alpha x d\alpha = 0, \quad |x| > 1, \quad (3.13)$$

$$\frac{1}{\pi} \int_0^{\infty} \alpha [\xi_1(\alpha) A_3^1(\alpha) + \xi_2(\alpha) A_4^1(\alpha)] \cos \alpha x d\alpha = 0,$$

where

$$\tau_1(\alpha) = \left[1 + \sum_{m=1}^2 L_{3m}^1 e^{\alpha\beta_{3m}^1} - \left(1 + \sum_{m=1}^2 L_{3m}^2 e^{\alpha\beta_{3m}^2} \right) \Delta_1 - \left(1 + \sum_{m=1}^2 L_{4m}^2 e^{\alpha\beta_{4m}^2} \right) \Delta_2 \right],$$

$$\tau_2(\alpha) = \left[1 + \sum_{m=1}^2 L_{4m}^1 e^{\alpha\beta_{4m}^1} - \left(1 + \sum_{m=1}^2 L_{3m}^2 e^{\alpha\beta_{3m}^2} \right) \Delta_3 - \left(1 + \sum_{m=1}^2 L_{4m}^2 e^{\alpha\beta_{4m}^2} \right) \Delta_4 \right],$$

$$\xi_1(\alpha) = \left[k_3^1 + \sum_{m=1}^2 k_m^1 L_{3m}^1 e^{\alpha\beta_{3m}^1} - \left(k_3^2 + \sum_{m=1}^2 k_m^2 L_{3m}^2 e^{\alpha\beta_{3m}^2} \right) \Delta_1 - \left(k_4^2 + \sum_{m=1}^2 k_m^2 L_{4m}^2 e^{\alpha\beta_{4m}^2} \right) \Delta_2 \right], \quad (3.14)$$

$$\xi_2(\alpha) = \left[k_4^1 + \sum_{m=1}^2 k_m^1 L_{4m}^1 e^{\alpha\beta_{4m}^1} - \left(k_3^2 + \sum_{m=1}^2 k_m^2 L_{3m}^2 e^{\alpha\beta_{3m}^2} \right) \Delta_3 - \left(k_4^2 + \sum_{m=1}^2 k_m^2 L_{4m}^2 e^{\alpha\beta_{4m}^2} \right) \Delta_4 \right],$$

$$\Delta_1 = \frac{E_4^2 D_3^1 - D_4^2 E_3^1}{\Delta}, \quad \Delta_2 = \frac{D_3^2 E_3^1 - E_3^2 D_3^1}{\Delta},$$

$$\Delta_3 = \frac{E_4^2 D_4^1 - D_4^2 E_4^1}{\Delta}, \quad \Delta_4 = \frac{D_3^2 E_4^1 - E_3^2 D_4^1}{\Delta}.$$

The unknown functions $A_j^1(\alpha)$ ($j = 3, 4$) can be determined through solving the integral equations (3.12) and (3.13) as follows [21].

Let

$$\lim_{y \rightarrow 0^+} \frac{\partial v^1(x, y)}{\partial x} - \lim_{y \rightarrow 0^-} \frac{\partial v^2(x, y)}{\partial x} = \phi_1(x) [1 - H(x - 1)],$$

$$\lim_{y \rightarrow 0^+} \frac{\partial u^1(x, y)}{\partial x} - \lim_{y \rightarrow 0^-} \frac{\partial u^2(x, y)}{\partial x} = \phi_2(x) [1 - H(x - 1)], \quad (3.15)$$

where $H(x - 1)$ is the unit step function [2], while $\phi_j(x)$ ($j = 1, 2$) are unknown odd and even functions of x , respectively.

From (3.13) and (3.15), one can deduce that

$$\begin{aligned} A_3^1(\alpha) &= \frac{\tau_2\Phi_1(\alpha) + \xi_2\Phi_2(\alpha)}{(\alpha\Psi)}, \\ A_4^1(\alpha) &= \frac{-[\tau_1\Phi_1(\alpha) + \xi_1\Phi_2(\alpha)]}{(\alpha\Psi)}, \end{aligned} \tag{3.16}$$

where

$$\begin{aligned} \Phi_1(\alpha) &= 2 \int_0^1 \phi_1(x) \sin \alpha x \, dx, \\ \Phi_2(\alpha) &= 2 \int_0^1 \phi_2(x) \cos \alpha x \, dx, \\ \Psi &= \tau_1\xi_2 - \tau_2\xi_1. \end{aligned} \tag{3.17}$$

Substituting (3.16) into (3.12), the problem is reduced to the following system of integral equations:

$$\sum_{j=1}^2 \int_{-1}^1 \check{H}_{ij}(x,t)\phi_j(t)dt = f_i(x), \quad |x| < 1, \quad i = 1, 2, \tag{3.18}$$

where the kernels $\check{H}_{ij}(x,t)$ are

$$\begin{aligned} \check{H}_{11}(x,t) &= \frac{1}{\pi} \int_0^\infty \frac{1}{\Psi} [E_3^1\tau_2 - E_4^1\tau_1] \sin \alpha(t-x) d\alpha, \\ \check{H}_{12}(x,t) &= \frac{1}{\pi} \int_0^\infty \frac{1}{\Psi} [E_3^1\xi_2 - E_4^1\xi_1] \cos \alpha(t-x) d\alpha, \\ \check{H}_{21}(x,t) &= \frac{1}{\pi} \int_0^\infty \frac{1}{\Psi} [D_3^1\tau_2 - D_4^1\tau_1] \cos \alpha(t-x) d\alpha, \\ \check{H}_{22}(x,t) &= -\frac{1}{\pi} \int_0^\infty \frac{1}{\Psi} [D_3^1\xi_2 - D_4^1\xi_1] \sin \alpha(t-x) d\alpha. \end{aligned} \tag{3.19}$$

Since the integrands of (3.19) are continuous functions of α , then it is clear that any possible singularity of the kernels must result from the asymptotic analysis of the integrands as $t \rightarrow x$ and $\alpha \rightarrow \infty$ [16, 21]. Then, by adding and subtracting the asymptotic expressions of these integrands under the integral sign, the problem can be reduced to the following pair of singular integral equations with Cauchy-type singularity:

$$\frac{1}{\pi} \sum_{j=1}^2 \left(\delta_{ij} G_{ij} \int_{-1}^1 \frac{\phi_j(t)}{t-x} dt + \int_{-1}^1 H_{ij}(x,t)\phi_j(t)dt \right) = f_i(x), \quad |x| < 1, \quad i = 1, 2, \tag{3.20}$$

where

$$\begin{aligned}
H_{11}(x,t) &= \int_0^\infty \left\langle \frac{1}{\Psi} [E_3^1 \tau_2 - E_4^1 \tau_1] - G_{11} \right\rangle \sin \alpha(t-x) d\alpha, \\
H_{12}(x,t) &= \int_0^\infty \left\langle \frac{1}{\Psi} [E_3^1 \xi_2 - E_4^1 \xi_1] - G_{12} \right\rangle \cos \alpha(t-x) d\alpha, \\
H_{21}(x,t) &= \int_0^\infty \left\langle \frac{1}{\Psi} [D_3^1 \tau_2 - D_4^1 \tau_1] - G_{21} \right\rangle \cos \alpha(t-x) d\alpha, \\
H_{22}(x,t) &= \int_0^\infty \left\langle \frac{-1}{\Psi} [D_3^1 \xi_2 - D_4^1 \xi_1] - G_{22} \right\rangle \sin \alpha(t-x) d\alpha, \\
G_{11} &= \frac{\langle o_3^1(B-s_2)/B - o_4^1(B-s_1)/B \rangle}{Z}, \\
G_{12} &= \frac{\langle o_3^1(k_4^1 B - s_4)/B - o_4^1(k_3^1 B - s_3)/B \rangle}{Z}, \\
G_{21} &= \frac{\langle p_3^1(B-s_2)/B - p_4^1(B-s_1)/B \rangle}{Z}, \\
G_{22} &= \frac{\langle p_4^1(k_3^1 B - s_3)/B - p_3^1(k_4^1 B - s_4)/B \rangle}{Z}, \\
Z &= (k_4^1 - k_3^1) + \frac{s_3 - s_4 + k_3^1 s_2 - k_4^1 s_1}{B} + \frac{s_1 s_4 - s_2 s_3}{B^2}, \\
B &= (L_{31}^2 L_{42}^2 - L_{41}^2 L_{32}^2) (p_1^2 o_2^2 - p_2^2 o_1^2), \\
s_1 &= (B_{13} + B_{24}) L_{31}^2 L_{42}^2 + (B_{12} + B_{27}) L_{41}^2 L_{32}^2, \\
s_2 &= (B_{33} + B_{44}) L_{31}^2 L_{42}^2 + (B_{32} + B_{47}) L_{41}^2 L_{32}^2, \\
s_3 &= (k_1^2 B_{13} + k_2^2 B_{24}) L_{31}^2 L_{42}^2 + (k_2^2 B_{12} + k_1^2 B_{27}) L_{41}^2 L_{32}^2, \\
s_4 &= (k_1^2 B_{33} + k_2^2 B_{44}) L_{31}^2 L_{42}^2 + (k_2^2 B_{32} + k_1^2 B_{47}) L_{41}^2 L_{32}^2, \\
B_{13} &= p_3^1 o_2^2 - p_2^2 o_3^1, & B_{24} &= p_1^2 o_3^1 - p_3^1 o_1^2, \\
B_{12} &= p_3^1 o_1^2 - p_1^2 o_3^1, & B_{27} &= p_2^2 o_3^1 - p_3^1 o_2^2, \\
B_{33} &= p_4^1 o_2^2 - p_2^2 o_4^1, & B_{44} &= p_1^2 o_4^1 - p_4^1 o_1^2, \\
B_{32} &= p_4^1 o_1^2 - p_1^2 o_4^1, & B_{47} &= p_2^2 o_4^1 - p_4^1 o_2^2.
\end{aligned} \tag{3.21}$$

From (3.15) and (2.5d), one can deduce the single-valuedness conditions ensuring the uniqueness of $\phi_i(\alpha)$ ($i = 1, 2$) as follows:

$$\int_{-1}^1 \phi_1(t) dt = 0, \quad \int_{-1}^1 \phi_2(t) dt = \frac{2}{c} \left(\sqrt{\frac{C_{11}^2}{m^2}} - \sqrt{\frac{C_{11}^1}{m^1}} \right). \tag{3.22}$$

Equations (3.20) and (3.22) can be solved as follows [17].

Assume that

$$\phi_i(t) = \frac{q_i(t)}{\sqrt{1-t^2}} \quad (i = 1, 2), \tag{3.23}$$

where $q_i(t)$ ($i = 1, 2$) are bounded continuous functions for all $t \in [-1, 1]$.

By substituting from (3.23) into (3.20) and (3.22) then employing Gauss-Chebyshev integration formulae, the solution of the problem can be reduced to the following system of linear algebraic equations [17]:

$$\sum_{j=1}^2 \sum_{k=1}^{n_1} \left(w_k \left[\frac{\delta_{ij} G_{ij}}{t_k - x_l} + H_{ij}(x_l, t_k) \right] q_j(t_k) \right) = f_i(x_l) \quad (i = 1, 2) \quad (x_l = 1, n_1 - 1),$$

$$\sum_{k=1}^{n_1} w_k q_1(t_k) = 0, \tag{3.24}$$

$$\sum_{k=1}^{n_1} w_k q_2(t_k) = \frac{2}{\pi c} \left(\sqrt{\frac{C_{11}^2}{m^2}} - \sqrt{\frac{C_{11}^1}{m^1}} \right),$$

where n_1 is the number of collocation points in the interval $[-1, 1]$,

$$w_1 = w_{n_1} = \frac{1}{2n_1 - 2}, \quad w_k = \frac{1}{n_1 - 1} \quad (\text{for } k = 2, n_1 - 1),$$

$$t_k = \cos \left(\frac{\pi(k-1)}{n_1 - 1} \right) \quad (k = 1, n_1), \tag{3.25}$$

$$x_l = \cos \left(\frac{\pi(2l-1)}{2n_1 - 2} \right) \quad (l = 1, n_1 - 1).$$

For the concerned problem, one can deduce that the DSIF at the left and right crack tips are equal. Then, by making use of the following asymptotic relations, as $\alpha \rightarrow \infty$, [5]:

$$\Phi_1(\alpha) = \int_{-1}^1 \frac{q_1(t)}{\sqrt{1-t^2}} \sin \alpha t \, dt \approx q_1(1) \sqrt{\frac{2\pi}{\alpha}} \sin \left(\alpha - \frac{\pi}{4} \right) + \vartheta \left(\frac{1}{\alpha} \right),$$

$$\Phi_2(\alpha) = \int_{-1}^1 \frac{q_2(t)}{\sqrt{1-t^2}} \cos \alpha t \, dt \approx q_2(1) \sqrt{\frac{2\pi}{\alpha}} \cos \left(\alpha - \frac{\pi}{4} \right) + \vartheta \left(\frac{1}{\alpha} \right), \tag{3.26}$$

$$\int_0^\infty \frac{1}{\sqrt{\alpha}} e^{-b\alpha} \left\{ \frac{\sin h\alpha}{\cos h\alpha} \right\} d\alpha = \frac{\sqrt{\pi}}{(b^2 + h^2)^{0.25}} \left\{ \frac{\sin}{\cos} \right\} \left(0.5 \tan^{-1} \left(\frac{h}{b} \right) \right), \quad b > 0,$$

the leading terms of the asymptotic stress field distribution (3.5) at the immediate vicinity of the right crack tip ($x \rightarrow 1$ and $y \rightarrow 0^\pm$) can be obtained as follows:

$$\begin{aligned}\sigma_{xy}(x, y) &\approx q_1(1) \left(\frac{\zeta_1}{\sqrt{2\rho_1}} \sin \frac{\theta_1}{2} - \frac{\zeta_2}{\sqrt{2\rho_2}} \sin \frac{\theta_2}{2} \right) \\ &\quad + q_2(1) \left(\frac{\zeta_3}{\sqrt{2\rho_1}} \cos \frac{\theta_1}{2} - \frac{\zeta_4}{\sqrt{2\rho_2}} \cos \frac{\theta_2}{2} \right), \\ \sigma_{yy}(x, y) &\approx q_1(1) \left(\frac{\gamma_1}{\sqrt{2\rho_1}} \cos \frac{\theta_1}{2} - \frac{\gamma_2}{\sqrt{2\rho_2}} \cos \frac{\theta_2}{2} \right) \\ &\quad + q_2(1) \left(\frac{\gamma_3}{\sqrt{2\rho_1}} \sin \frac{\theta_1}{2} - \frac{\gamma_4}{\sqrt{2\rho_2}} \sin \frac{\theta_2}{2} \right),\end{aligned}\tag{3.27}$$

where

$$\begin{aligned}\rho_1 &= \sqrt{(x-1)^2 + (r_3^1 y)^2}, & \rho_2 &= \sqrt{(x-1)^2 + (r_4^1 y)^2}, \\ \theta_1 &= \tan^{-1} \left(\frac{r_3^1 y}{x-1} \right), & \theta_2 &= \tan^{-1} \left(\frac{r_4^1 y}{x-1} \right), \\ \xi_1 &= \frac{p_3^1(1-s_2/B)}{Z}, & \xi_2 &= \frac{p_4^1(1-s_1/B)}{Z}, \\ \xi_3 &= \frac{p_3^1(k_4^1-s_4/B)}{Z}, & \xi_4 &= \frac{p_4^1(k_3^1-s_3/B)}{Z}, \\ \gamma_1 &= \frac{o_3^1(1-s_2/B)}{Z}, & \gamma_2 &= \frac{o_4^1(1-s_1/B)}{Z}, \\ \gamma_3 &= \frac{o_3^1(k_4^1-s_4/B)}{Z}, & \gamma_4 &= \frac{o_4^1(k_3^1-s_3/B)}{Z}.\end{aligned}\tag{3.28}$$

Therefore, the DSIF, K_I , and K_{II} can be determined as follows [18]:

$$K_I + iK_{II} = Q\sqrt{2a_0} \lim_{x \rightarrow 1, y \rightarrow 0^+} \sqrt{x-1} [\sigma_{yy}(x, y) + i\sigma_{xy}(x, y)]\tag{3.29}$$

such that by substituting from (3.27) and (3.28) into (3.29) then evaluating the limits, one can find that

$$\begin{aligned}K_I &= Q\sqrt{a_0}[\gamma_1 - \gamma_2]q_1(1), \\ K_{II} &= Q\sqrt{a_0}[\xi_3 - \xi_4]q_2(1).\end{aligned}\tag{3.30}$$

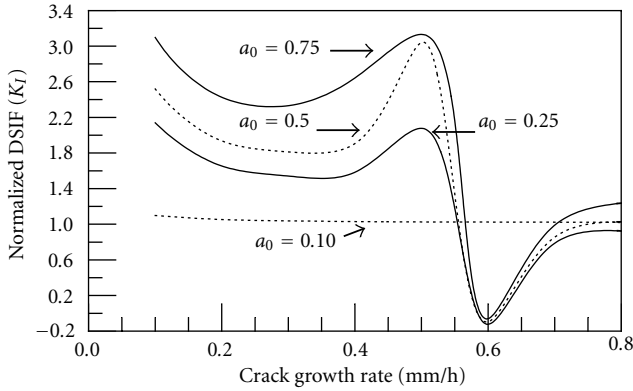


Figure 4.1. Variation of the normalized K_I with the crack growth rate and initial crack length.

4. Numerical results

A parametric study is introduced to investigate the effects of crack growth rate, initial crack length, and the plate width on the values of DSIF. Consider that a structure of two bonded orthotropic plates as in Figure 1.1 possesses the following elastic characteristics:

$$\begin{aligned}
 m^1 &= m^2 = 1\text{g/cm}^3, \\
 C_{66}^1 &= C_{66}^2 = 1\text{MPa}, \\
 C_{22}^1 &= 2.5\text{MPa}, \\
 C_{22}^2 &= 4\text{MPa}, \\
 C_{11}^\ell &= (1 + r_1^\ell)C_{66}^\ell - r_1^\ell (r_2^\ell)^2 C_{22}^\ell \quad (\ell = 1, 2), \\
 C_{12}^\ell &= \left[\sqrt{r_1^\ell [(r_2^\ell)^2 + 1]} - [(r_1^\ell)^2 + (r_2^\ell)^2] - 1 \right] C_{66}^\ell \quad (\ell = 1, 2),
 \end{aligned}
 \tag{4.1}$$

where (4.1) are derived from (2.5), (3.2), and (3.3). Also, for the concerned numerical results, it is assumed that $1 > r_1^\ell > r_2^\ell > 0$, $r_3^\ell = -r_1^\ell$, and $r_4^\ell = -r_2^\ell$. The initial crack length $2a_0$ ranges from 0.2 to 1.5 cm, while the width of plates ranges from 5 to 10 m. For simplicity, the numerical results are obtained for constant uniform stress distribution along the crack surfaces, $|x| < 1$ and $y \rightarrow \pm 0$.

Furthermore, we have found that $|\int_0^\infty I_{ij}(\alpha, x, t) d\alpha - \int_0^4 I_{ij}(\alpha, x, t) d\alpha| < 10^{-16}$, where $I_{i,j}(\alpha, x, t)$ ($i, j = 1, 2$), are the integrands of (3.21). Therefore, the improper integrals of (3.21) are approximated and evaluated numerically from $\alpha = 0 \rightarrow 4$ by using the trapezoidal rule. Then, the values of DSIF are normalized such that

$$\text{Normalized } K_I = \frac{K_I}{\sigma_{22}^1 \sqrt{a_0}}, \quad \text{Normalized } K_{II} = \frac{K_{II}}{\sigma_{12}^1 \sqrt{a_0}}, \tag{4.2}$$

where σ_{22}^1 and σ_{12}^1 represent the applied stress along the upper crack surface.

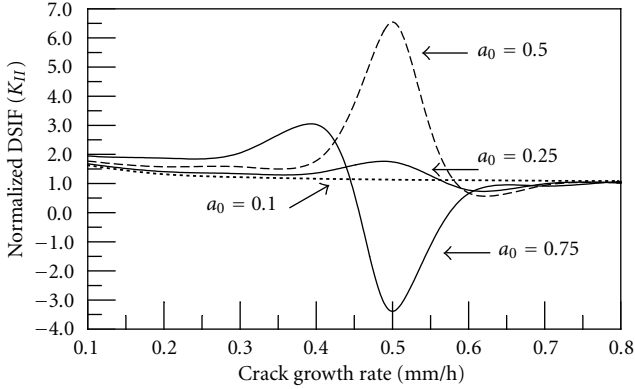


Figure 4.2. Variation of the normalized K_{II} with the crack growth rate and initial crack length.

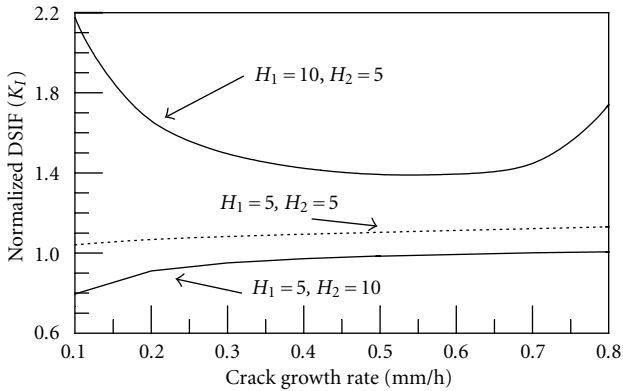


Figure 4.3. Variation of the normalized K_I with the crack growth rate for different plate widths.

Figure 4.1 shows that the value of normalized K_I continuously decreases with increasing the crack growth rate, where $0 < c < 0.32$ and $0.5 < c < 0.6$, while it increases elsewhere. Also, it shows increasing the pathological oscillatory behaviour [3] for the normalized K_I with increasing the initial crack length.

Figure 4.2 shows that the value of normalized K_{II} continuously increases with increasing the crack growth rate except for $0.5 < c < 0.65$. But this decreasing interval is shifted to $0.4 < c < 0.5$ for the case of a relatively long initial crack length $2a_0 = 1.5$ cm. One can notice as well that the pathological oscillatory behaviour of the normalized K_{II} increases with increasing a_0 .

For the prescribed elastic and geometric characteristics, Figure 4.3 shows that the value of normalized K_I continuously increases with increasing the crack growth rate except when $c < 0.5$ and $H_1 > H_2$, it is decreased. Also, Figure 4.4 shows that the value of normalized K_{II} continuously decreases with increasing the crack growth rate, while it increases with increasing c when $c > 0.62$ and $H_1 < H_2$.

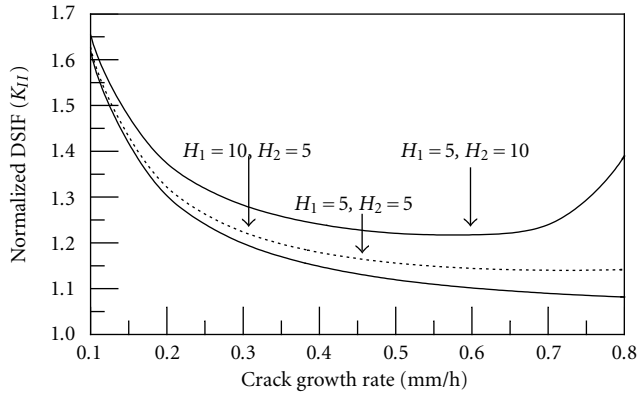


Figure 4.4. Variation of the normalized K_{II} with the crack growth rate for different plate widths.

5. Conclusion

The present work is concerned with elastodynamic analysis of crack propagation between two bonded dissimilar orthotropic plates. The width of each plate is assumed to be finite. This is the new trend and the main difference between this work and the previous ones [1, 3, 4, 6, 7, 8, 10, 12, 13, 14, 15, 19, 20, 22, 23]. So, the present work can be considered as an extension for the analysis of interfacial crack problems.

References

- [1] R. Babaei and S. A. Lukasiewicz, *Dynamic response of a crack in a functionally graded material between two dissimilar half planes under antiplane shear impact*, *Engng. Fracture Mech.* **60** (1998), 479–487.
- [2] R. N. Bracewell, *The Fourier Transform and Its Applications*, McGraw-Hill Series in Electrical Engineering, Circuits and Systems, McGraw-Hill, New York, 1986.
- [3] S. Das and B. Patra, *Moving Griffith crack at the interface of two dissimilar orthotropic half planes*, *Engng. Fracture Mech.* **54** (1996), 523–531.
- [4] ———, *Stress intensity factors for moving interfacial crack between bonded dissimilar fixed orthotropic layers*, *Comput. & Structures* **69** (1998), no. 4, 459–472.
- [5] F. Delale and F. Erdogan, *Transverse shear effect in a circumferentially cracked cylindrical shell*, *Quart. Appl. Math.* **37** (1979), 239–258.
- [6] A. H. England, *A crack between dissimilar media*, *Trans. ASME J. Appl. Mech.* **32** (1965), 400–402.
- [7] F. Erdogan and G. Gupta, *Layered composites with an interface flaw*, *Internat. J. Solids Structures* **7** (1971), 1089–1107.
- [8] F. Erdogan and B. Wu, *Interface crack problems in layered orthotropic materials*, *J. Mech. Phys. Solids* **41** (1993), no. 5, 889–917.
- [9] R. F. Gibson, *Principles of Composite Material Mechanics*, McGraw-Hill, New York, 1994.
- [10] S. Itou, *Dynamic stress intensity factors around two rectangular cracks in a half-space under impact load*, *Acta Mech.* **121** (1997), no. 1–4, 153–164.
- [11] J. F. Kalthoff, J. Beinert, and S. Winkler, *Measurements of dynamic stress intensity factors for fast running cracks in double-cantilever-beam specimens*, *Fast Fracture and Crack Arrest* (G. T. Hahn and M. F. Kanninen, eds.), ASTM STP, vol. 627, American Society for Testing and Materials, Pennsylvania, 1977, pp. 161–176.

- [12] K. H. Lee, *Stress and displacement fields for propagating the crack along the interface of dissimilar orthotropic materials under dynamic mode I and mode II load*, Trans. ASME J. Appl. Mech. **67** (2000), 223–228.
- [13] K. H. Lee, J. S. Hawong, and S. H. Choi, *Dynamic stress intensity factors K_I , K_{II} and dynamic crack propagation characteristics of orthotropic material*, Engrg. Fracture Mech. **53** (1996), 119–140.
- [14] J. Y. Liou and J. C. Sung, *Singularities at the tip of a crack terminating normally at an interface between two orthotropic media*, Trans. ASME J. Appl. Mech. **63** (1996), 264–270.
- [15] C.-C. Ma and Y.-S. Ing, *Dynamic crack propagation in a layered medium under antiplane shear*, Trans. ASME J. Appl. Mech. **64** (1997), no. 1, 66–72.
- [16] M. S. Matbuly, *Mode II stress intensity factor for cracked layered material*, The 3rd International Conference on Engineering Mathematics and Physics (Cairo, Egypt), Faculty of Engineering, Cairo University, Cairo, 1997, pp. 801–808.
- [17] M. S. Matbuly, S. A. Mohamed, and M. Nassar, *On the numerical solution of the first kind singular integral equations*, The 3rd International Conference on Engineering Mathematics and Physics (Cairo, Egypt), Faculty of Engineering, Cairo University, Cairo, 1997, pp. 11–17.
- [18] V. Z. Parton and E. M. Morozov, *Elastic-Plastic Fracture Mechanics*, Mir Publishers, Moscow, 1978.
- [19] J. R. Rice, *Elastic fracture mechanics concepts for interfacial cracks*, Trans. ASME J. Appl. Mech. **55** (1988), 98–103.
- [20] C. Rubio-Gonzalez and J. J. Mason, *Response of finite cracks in orthotropic materials due to concentrated impact shear loads*, Trans. ASME J. Appl. Mech. **66** (1999), no. 2, 485–491.
- [21] N. I. Shbeeb, W. K. Binienda, and K. L. Kreider, *Analysis of the driving forces for multiple cracks in an infinite non-homogeneous plate, part I: theoretical analysis*, Trans. ASME J. Appl. Mech. **66** (1999), no. 2, 492–500.
- [22] M. Valentini, S. K. Serkov, D. Bigoni, and A. B. Movchan, *Crack propagation in a brittle elastic material with defects*, Trans. ASME J. Appl. Mech. **66** (1999), 79–86.
- [23] B. L. Wang, J. C. Han, and S. Y. Du, *Dynamic response for non-homogeneous piezoelectric medium with multiple cracks*, Engrg. Fracture Mech. **61** (1998), 607–617.

M. S. Matbuly: Department of Engineering Mathematics and Physics, Faculty of Engineering, Zagazig University, P.O. 44519, Zagazig, Egypt
E-mail address: mohamedmatbuly@hotmail.com

Special Issue on Space Dynamics

Call for Papers

Space dynamics is a very general title that can accommodate a long list of activities. This kind of research started with the study of the motion of the stars and the planets back to the origin of astronomy, and nowadays it has a large list of topics. It is possible to make a division in two main categories: astronomy and astrodynamics. By astronomy, we can relate topics that deal with the motion of the planets, natural satellites, comets, and so forth. Many important topics of research nowadays are related to those subjects. By astrodynamics, we mean topics related to spaceflight dynamics.

It means topics where a satellite, a rocket, or any kind of man-made object is travelling in space governed by the gravitational forces of celestial bodies and/or forces generated by propulsion systems that are available in those objects. Many topics are related to orbit determination, propagation, and orbital maneuvers related to those spacecrafts. Several other topics that are related to this subject are numerical methods, nonlinear dynamics, chaos, and control.

The main objective of this Special Issue is to publish topics that are under study in one of those lines. The idea is to get the most recent researches and published them in a very short time, so we can give a step in order to help scientists and engineers that work in this field to be aware of actual research. All the published papers have to be peer reviewed, but in a fast and accurate way so that the topics are not outdated by the large speed that the information flows nowadays.

Before submission authors should carefully read over the journal's Author Guidelines, which are located at <http://www.hindawi.com/journals/mpe/guidelines.html>. Prospective authors should submit an electronic copy of their complete manuscript through the journal Manuscript Tracking System at <http://mts.hindawi.com/> according to the following timetable:

Manuscript Due	July 1, 2009
First Round of Reviews	October 1, 2009
Publication Date	January 1, 2010

Lead Guest Editor

Antonio F. Bertachini A. Prado, Instituto Nacional de Pesquisas Espaciais (INPE), São José dos Campos, 12227-010 São Paulo, Brazil; prado@dem.inpe.br

Guest Editors

Maria Cecilia Zanardi, São Paulo State University (UNESP), Guaratinguetá, 12516-410 São Paulo, Brazil; cecilia@feg.unesp.br

Tadashi Yokoyama, Universidade Estadual Paulista (UNESP), Rio Claro, 13506-900 São Paulo, Brazil; tadashi@rc.unesp.br

Silvia Maria Giuliatti Winter, São Paulo State University (UNESP), Guaratinguetá, 12516-410 São Paulo, Brazil; silvia@feg.unesp.br